

RI 9321

**RI 9321**

**REPORT OF INVESTIGATIONS/1990**

PLEASE DO NOT REMOVE FROM LIBRARY

# **Infrared Spectroscopic Study of the Flocculation of Zinc and Copper Precipitates**

**By Frank J. Susko and B. J. Scheiner**

1910 ★ **80** ★ 1990  
YEARS

**BUREAU OF MINES**



**UNITED STATES DEPARTMENT OF THE INTERIOR**

U.S. Bureau of Mines  
Research Center  
1415 North 17th Ave.  
Denver, CO 80202  
303-439-9000

**Mission:** As the Nation's principal conservation agency, the Department of the Interior has responsibility for most of our nationally-owned public lands and natural and cultural resources. This includes fostering wise use of our land and water resources, protecting our fish and wildlife, preserving the environmental and cultural values of our national parks and historical places, and providing for the enjoyment of life through outdoor recreation. The Department assesses our energy and mineral resources and works to assure that their development is in the best interests of all our people. The Department also promotes the goals of the Take Pride in America campaign by encouraging stewardship and citizen responsibility for the public lands and promoting citizen participation in their care. The Department also has a major responsibility for American Indian reservation communities and for people who live in Island Territories under U.S. Administration.

**Report of Investigations 9321**

# **Infrared Spectroscopic Study of the Flocculation of Zinc and Copper Precipitates**

**By Frank J. Susko and B. J. Scheiner**

**UNITED STATES DEPARTMENT OF THE INTERIOR  
Manuel Lujan, Jr., Secretary**

**BUREAU OF MINES  
T S Ary, Director**

---

This report is based upon work done under an agreement between the University of Alabama and the Bureau of Mines.

**Library of Congress Cataloging in Publication Data:**

**Susko, Frank J.**

Infrared spectroscopic study of the flocculation of zinc and copper precipitates /  
by Frank J. Susko and B. J. Scheiner.

p. cm. -- (Report of investigations; 9321)

Includes bibliographical references: (p. 5)

Supt. of Docs. no.: I 28.23:9321.

1. Flocculation. 2. Infrared spectroscopy. 3. Precipitation (chemistry).  
I. Scheiner, Bernard J. II. Title. III. Series: Report of investigations (United  
States. Bureau of Mines); 9321.

TN23.U43 [QD547] 622 s-dc20 [622'.7] 90-2102 CIP

## CONTENTS

	<i>Page</i>
Abstract .....	1
Introduction .....	2
Background .....	2
Experimental Procedure .....	2
Results and Discussion .....	3
Conclusions .....	5
References .....	5

## ILLUSTRATIONS

1. Molecular structures of polymers used as flocculants .....	3
2. IR spectra of Zn(OH) <sub>2</sub> and Cu(OH) <sub>2</sub> .....	3
3. IR spectra of ZnS precipitate before and after heating .....	4

## TABLES

1. Hydroxyl stretching band frequencies for metal precipitates treated with polymer .....	3
2. Water bending band frequencies for metal precipitates treated with polymer .....	3
3. Area of frequency bands describing water for IR tests of ZnS, Zn(OH) <sub>2</sub> , and Cu(OH) <sub>2</sub> precipitates ....	4
4. Organic group frequency band assignments of polymers and polymer-treated precipitates .....	4

### UNIT OF MEASURE ABBREVIATIONS USED IN THIS REPORT

°C degree Celsius

cm centimeter

cm<sup>-1</sup> wavenumber

g gram

g/L gram per liter

h hour

min minute

mL milliliter

pct percent

# INFRARED SPECTROSCOPIC STUDY OF THE FLOCCULATION OF ZINC AND COPPER PRECIPITATES

By Frank J. Susko<sup>1</sup> and B. J. Scheiner<sup>2</sup>

---

## ABSTRACT

The U.S. Bureau of Mines is developing a process for removing metals from mining and mineral processing waste streams by precipitation. The precipitation process is accelerated by flocculation when a high molecular weight polymer is added. Infrared (IR) studies were performed on zinc hydroxide [Zn(OH)<sub>2</sub>], copper hydroxide [Cu(OH)<sub>2</sub>], and zinc sulfide (ZnS) flocculated with both nonionic and anionic polyacrylamide (PAM) and polyethylene oxide (PEO). The IR data were compared with general trends in the performance of the polymers observed during flocculation. These studies will help to understand the bonding between the precipitate and polymer and indicate the effectiveness of a flocculant for dewatering.

Two types of bands showed up on the IR spectra; one type described the interlayer water of the flocs, the other described the organic bonds of the polymers. A general decrease in the areas of the three water bands, hydroxyl (O-H) stretching (3,200-3,500 cm<sup>-1</sup>), water bending (1,610-1,630 cm<sup>-1</sup>), and torsional oscillations (600-700 cm<sup>-1</sup>), indicate interlayer water being driven off, which is a favorable condition in flocculation. Shifts in the O-H stretching band indicate water bridging between the precipitate and polymer. Shifts in the amine (N-H) deformation, carbon-nitrogen (C-N) stretch band (1,600-1,610 cm<sup>-1</sup>) indicate the amine group of the PAM is involved in the bonding. Evidence suggests that ether oxygen of PEO is also involved in the bonding process.

---

<sup>1</sup>Chemical engineer.

<sup>2</sup>Supervisory metallurgist.

Tuscaloosa Research Center, U.S. Bureau of Mines, Tuscaloosa, AL.

## INTRODUCTION

Mining and mineral processing operations often produce waste streams that contain dissolved metal ions. These waste stream metal ions pose an environmental threat and are also a potential source of valuable metals. The usual practice of dealing with these waste streams is to precipitate the metal ions with lime. However, the resulting sludge retains large amounts of water and filters poorly. The use of flocculants in the mining and mineral industry is well documented, but the application of flocculating agents for metal hydroxide sludges has received little attention. As a result, the U.S. Bureau of Mines has been investigating the removal of metals from mining and mineral processing waste streams. The study involved the precipitation of metals such as zinc and copper with hydroxyl or sulfide ion. The resulting precipitate contained large quantities of water and settled slowly. Flocculation of the precipitates with high molecular weight polymer accelerated the settling. In previous research, the Bureau developed a flocculation technique for a variety of mineral slurries using PEO as the flocculating agent (1).<sup>3</sup> As part of the research, IR spectroscopy was used to determine the type of association between the polymer and montmorillonite clays (2). It was determined that characteristic shifts occur in the frequency bands of the IR spectra when an organic molecule is adsorbed onto the surface of a clay mineral. Interpreting the shifts in the frequency bands can give insight into the mode of attachment between the polymer and clay surface. In this report, IR spectroscopy was applied to the study of zinc and copper precipitates treated with PAM and PEO. The IR spectra of the zinc and copper precipitates with and without addition of various polymers were studied. The spectra was compared with general trends in the polymers' performance as flocculating agents. These studies will help to understand the bonding between the precipitate and polymer and determine the effectiveness of a flocculant for dewatering.

### BACKGROUND

For IR spectra obtained from flocculating mineral slurries, the analysis of the coordinated water bands before and after flocculation are of major interest. Several articles described the possible spectral bands for water associated with mineral slurries (2-7). Two of these types of bands are the O-H stretching, appearing between 3,200 and 3,500  $\text{cm}^{-1}$ , and the water bending, appearing between 1,610 and 1,630  $\text{cm}^{-1}$  (3). These bands are due to water molecules coordinated in the crystal lattice. The area of the water bending band is related to the amount of water present in the interlayer region (2-3). It has been reported that heating the mineral removes the interlayer water and has been illustrated on an IR spectra by a decrease in the area of the water bending band (4). It has also been

reported that a shift in the water bending band to a higher wave number occurs upon addition of polymer. The shift was due to the polymer's influence on the water of hydration, indicating the polymer's interaction with the cation of montmorillonite through a water bridge (2). Another frequency band shift involving the O-H stretching where an increase in hydrogen bonding produces a shift in the O-H stretching band to a lower frequency has been reported (5). A third water band occurs around 600  $\text{cm}^{-1}$  and has been reported as the torsional oscillations band (3, 6-7). This band is due to the hindered rotations of the water molecule locked in the lattice structure resulting in oscillations of the entire molecule.

Several articles have also dealt with vibrational assignments of metal-organic bonds such as the metal-amine frequency band assignment in a copper-urea complex (7-9). The N-H bending and C-N stretching frequencies of urea shifted to a lower wave number upon complexation with copper. The frequency shifts were due to the complexation of copper through the nitrogen of the amine group. Other investigations showed that when copper is reacted with acetylacetone, a complex is formed with carbonyl groups and a carbonyl band shift from 1,610 to 1,580  $\text{cm}^{-1}$  is observed (8).

Previous research conducted by the Bureau has shown that when PEO is reacted with montmorillonite, certain shifts in the IR spectra are observed. These shifts were due to the adsorptions of PEO onto montmorillonite clays via the exchange ion of the clay. The methylene ( $\text{CH}_2$ ) symmetric-antisymmetric band of PEO at 2,880  $\text{cm}^{-1}$  shifted to a higher wave number upon adsorption. The hydrophobic nature of  $\text{CH}_2$  lead to the adsorption onto the magnesium ion of magnesium exchanged montmorillonite (2). The ether group of PEO could be considered a weak proton acceptor and was another possible site of adsorption (9).

### EXPERIMENTAL PROCEDURE

Solutions of zinc chloride and copper chloride with metal concentrations of 2.0 g/L were treated with stoichiometric amounts of calcium hydroxide or sodium sulfide. The precipitants were added all at once, stirred for 5 min, then allowed to settle for 5 min. The resulting precipitate was flocculated with nonionic PAM, anionic PAM (34 pct hydrolyzed) or PEO at concentrations of 0.075 and 0.60 g of polymer per liter of solution. The polymer was added slowly and mixed for 5 min. A control test was also run for both metals by adding deionized water instead of polymer. The molecular structures of the three polymers are illustrated in figure 1. The reagents used were analytical grade and were obtained from various commercial sources.

The following procedure, used to prepare the samples for IR analysis, was similar to one developed for ion-exchanged montmorillonite treated with PEO (2). A 0.1-mL sample from each of the untreated and

<sup>3</sup>Italic numbers in parentheses refer to items in the list of references at the end of this report.

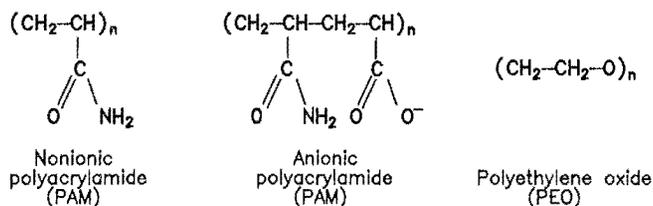


Figure 1.—Molecular structures of polymers used as flocculants.

polymer-treated precipitate suspensions was dried overnight on a silver chloride plate (2.5 by 1.3 by 0.05 cm) in a desiccator over calcium sulfate at atmospheric pressure and room temperature. A 0.1-mL sample of each of the

polymers was prepared in the same manner. Each of the dried samples was scanned using a Perkin Elmer<sup>4</sup> 684 IR spectrophotometer. The instrument was run at medium slit width with a 5 min scan time and in percent transmission mode. Resolution was set at 1 cm<sup>-1</sup> and an average of three scans were taken for each sample. The samples were automatically scanned from 4,000 to 400 cm<sup>-1</sup> using a Perkin Elmer 3600 data station. Noise was removed from the resulting spectra using a five-point smoothing routine provided with the data station. The location and areas of the frequency bands were determined using software also provided with the data station.

<sup>4</sup>Reference to specific products does not imply endorsement by the U.S. Bureau of Mines.

## RESULTS AND DISCUSSION

Two types of bands showed up on the IR spectra. One type described coordinated water of the floccs; the other described the organic groups of the polymers.

Three frequency bands describing interlayer water appeared on the spectra. They were the O-H stretching (which occurred at approximately 3,200-3,400 cm<sup>-1</sup>), water bending vibration (1,610-1,625 cm<sup>-1</sup>), and torsional oscillations (600-700 cm<sup>-1</sup>). To study these bands, the spectra of the metal precipitates, shown in figures 2 and 3, were compared with the spectra of the precipitates treated with the different polymers.

The O-H stretching band frequencies from the spectra of the three flocculated precipitates are listed in table 1. In each case, the band shifted to a lower frequency upon addition of any of the polymers. This shift is an indication of an increase in hydrogen bonding (5). The increase in hydrogen bonding indicates greater stability of the precipitate and indicates the involvement of water bridge between the precipitate and the polymer (5).

Table 1.—Hydroxyl stretching band frequencies for metal precipitates treated with polymer, wavenumber

Polymer	Zn(OH) <sub>2</sub>	Cu(OH) <sub>2</sub>	ZnS
Control <sup>1</sup> . . . . .	3,443	3,441	3,523
Nonionic PAM . .	3,411	3,336	3,507
Anionic PAM . . .	3,427	3,336	3,512
PEO . . . . .	3,432	3,336	3,507

<sup>1</sup>Precipitate without polymer.

The water bending band frequencies from the spectra of zinc hydroxide, copper hydroxide, and zinc sulfide are shown in table 2. The results show that there were no band shifts in either the zinc hydroxide or the copper hydroxide tests. The spectra of the zinc sulfide showed a small shift in the water bending vibration for each of the polymers tested. Webb (2) reported this type of shift is due to water molecules acting as a bridge between the exchange ion of montmorillonite and the polymer PEO.

The shift in the case of zinc sulfide is most likely due to water molecules acting as a bridge between the metal specie of the precipitate and the polymer. The reason for not observing a shift for the copper and zinc hydroxide can be explained by the spectra shown in figure 2. The hydroxyl ions of the metal precipitates have a band peak at 1,627 cm<sup>-1</sup> that would mask the band shift.

Table 2.—Water bending band frequencies for metal precipitates treated with polymer, wavenumber

Polymer	Zn(OH) <sub>2</sub>	Cu(OH) <sub>2</sub>	ZnS
Control <sup>1</sup> . . . . .	1,627	1,627	1,612
Nonionic PAM . .	1,627	1,627	1,616
Anionic PAM . . .	1,627	1,627	1,616
PEO . . . . .	1,627	1,627	1,616

<sup>1</sup>Precipitate without polymer.

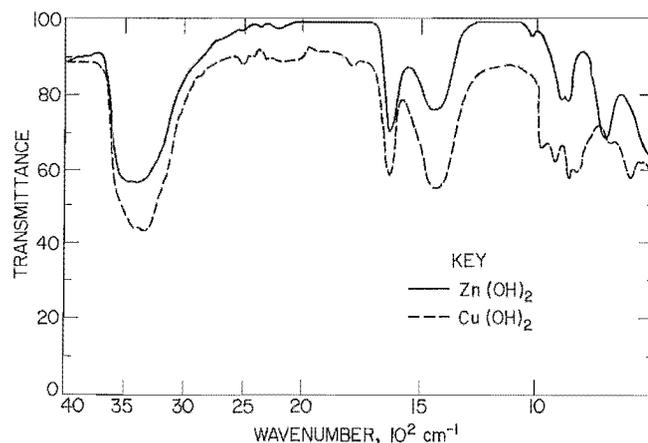


Figure 2.—IR spectra of Zn(OH)<sub>2</sub> and Cu(OH)<sub>2</sub>.



Three bands dominated the spectra for the nonionic PAM-metal precipitate flocculation: carbonyl (C=O) stretch ( $1,660\text{ cm}^{-1}$ ); N-H deformation, C-N stretch ( $1,610\text{ cm}^{-1}$ ); and  $\text{CH}_2$  deformation ( $1,450\text{ cm}^{-1}$ ). The N-H deformation-C-N stretch showed a frequency band shift for both metal hydroxides. This is similar to the frequency shift described in the literature for metal-amine assignments in copper-urea complexes (7). Urea showed a shift in the C-N stretching frequency band upon complexation with copper to a lower frequency due to the formation of a stronger C-N single bond, thus indicating the coordination of copper through the nitrogen of the amine group. A similar interaction takes place between the amine group of the nonionic PAM and the metal hydroxide. The electron pair of the nitrogen atom, acting as a weak proton acceptor, is the most likely site of attachment. The C=O stretch showed no frequency band shift. Similar results have been reported for the copper complex of polyamide where no shift in the carbonyl frequency band was observed, thus, indicating the carbonyl group's lack of involvement in the bonding. Since no shift in the carbonyl frequency was observed for the metal hydroxide - PAM spectra, it can be assumed that carbonyl plays no role in the flocculation. A similar argument can be made for the  $\text{CH}_2$  groups of the nonionic PAM since no shift was observed. The results of the anionic PAM test were very similar. The N-H deformation-C-N stretching vibration band shifted to a lower number indicating, again, the amide group is involved in the bonding. Two new bands

appeared that were the antisymmetric  $\text{CO}_2$  ( $1,560\text{ cm}^{-1}$ ) and symmetric  $\text{CO}_2$  ( $1,410\text{ cm}^{-1}$ ). These frequencies are due to the carboxyl group. Neither frequency band showed a shift, indicating this group of the polymer is not involved in the bonding. As with nonionic PAM, the C=O stretch and the  $\text{CH}_2$  deformation showed no band shift, indicating neither the carbonyl of the amide group nor the polymer chain is involved in the adsorption of the polymer.

Five group frequency bands dominated the spectra for PEO. They were  $\text{CH}_2$  symmetric-antisymmetric ( $2,880\text{ cm}^{-1}$ ), carbon-oxygen (C-O) stretch ( $1,140, 1,100, 1,060\text{ cm}^{-1}$ ), and  $\text{CH}_2$  rock-twist ( $960\text{ cm}^{-1}$ ). These bands appeared in the spectra of the flocculated copper hydroxide, but it is unknown why the bands did not appear in the spectra of the zinc hydroxide tests. There is a shift in the  $2,880\text{ cm}^{-1}$  band when PEO was adsorbed onto magnesium montmorillonite due to the  $\text{CH}_2$  being sufficiently hydrophobic to adsorb onto the magnesium ion (2). However, for flocculated copper hydroxide, no band shift was observed. The spectra also showed that no band shift was observed for the  $\text{CH}_2$  rock-twist band at  $960\text{ cm}^{-1}$  and the C-O stretching bands. Although the analysis of the O-H stretching bands study indicates some interaction between polymer and precipitate, the lack of a frequency band shift indicates a very weak interaction. The interaction for PEO with the metal precipitate is probably through the ether oxygen similar to the nitrogen atom of the amide group on PAM. A more detailed investigation is required to confirm the role of PEO in this type of flocculation system.

## CONCLUSIONS

The bonding of PAM and PEO on zinc and copper hydroxides was observed by studying the IR spectra of the flocculated precipitates. The spectra indicated bonding occurred at the nitrogen atom of PAM. The spectra also indicated the ether oxygen is the most likely site for bonding of PEO. The flocculant-metal precipitate matrix was stabilized by a water bridge for all polymers investigated. The spectra also showed a general decrease in the area of the three water bands, hydroxyl stretching, water bending, and torsional oscillations, indicating

interlayer water was replaced during the flocculation sequence. However, during tests using PAM as the flocculant, a greater replacement of water was evident by the general decrease in area of water bands when compared with PEO flocculated material. This parallels observations that showed PAM as a superior flocculant over PEO for dewatering metal precipitates. This investigation shows how IR analysis can be instrumental in determining a flocculant's effectiveness for dewatering.

## REFERENCES

1. Scheiner, B. J., A. G. Smelley, and D. A. Stanley. Dewatering of Mineral Waste Using the Flocculant Polyethylene Oxide. BuMines B 681, 1986, 18 pp.
2. Webb, S. W., D. A. Stanley, and B. J. Scheiner. An Infrared Examination of Ion-Exchanged Montmorillonite Treated With Polyethylene Oxide. BuMines RI 9036, 1986, 16 pp.
3. Nakamoto, K. Infrared Spectra of Inorganic and Coordination Compounds. Wiley (New York), 3d ed., 1978, 448 pp.
4. Little, L. H. Infrared Spectra of Adsorbed Species. Academic, 1966, pp. 334-351.
5. Kendall, D. N. (ed.). Applied Infrared Spectroscopy. Reinhold, 1966, p. 72.
6. Miller, F. A., G. L. Carlson, F. F. Bentley, and W. H. Jones. Infrared Spectra of Inorganic Ions in the Cesium Bromide Region ( $700\text{-}300\text{ cm}^{-1}$ ). Spectrochim Acta, v. 16, 1960, pp. 159-160.
7. Gupta, A. S., P. C. Srivastava, C. Aravindakshan, and B. K. Banerjee. X-Ray and Infrared Studies of a Copper-Urea Compound. J. Phys. Chem. Solids, v. 43, 1982, pp. 645-650.
8. Holtzclaw, H. F., Jr., and J. P. Collman. Infrared Absorption of Metal Chelate Compounds of 1,3-Diketones. J. Am. Chem. Soc., v. 79, 1957, pp. 3318-3322.
9. Brown, P. M., D. A. Stanley, and B. J. Scheiner. An Explanation of Flocculation Using Lewis Acid-Base Theory. AIME-SME preprint 88-165, 1988, 5 pp.
10. Sadtler Research Laboratory (Philadelphia, PA). The Infrared Spectra Atlas of Monomers and Polymers. 1980, pp. 387, 467.
11. Pappalardo, S., and F. Bottino. Novel Polyamides With Acyclic and Cyclic Bipyridyl Diamino Structures in the Polymer Backbone: Synthesis and Complexation with Transition Metals. J. Polymer Sci.: Part A: Polymer Chemistry, v. 25, 1987, pp. 1793-1801.